

11-11-2011

## Structure-property coupling in Sr<sub>3</sub>(Ru<sub>1-x</sub>Mn<sub>x</sub>)<sub>2</sub>O<sub>7</sub>

Biao Hu

*Louisiana State University*

Gregory T. McCandless

*Louisiana State University*

V. O. Garlea

*Oak Ridge National Laboratory*

S. Stadler

*Louisiana State University*

Yimin Xiong

*Louisiana State University*

*See next page for additional authors*

Follow this and additional works at: [https://digitalcommons.lsu.edu/physics\\_astronomy\\_pubs](https://digitalcommons.lsu.edu/physics_astronomy_pubs)

---

### Recommended Citation

Hu, B., McCandless, G., Garlea, V., Stadler, S., Xiong, Y., Chan, J., Plummer, E., & Jin, R. (2011). Structure-property coupling in Sr<sub>3</sub>(Ru<sub>1-x</sub>Mn<sub>x</sub>)<sub>2</sub>O<sub>7</sub>. *Physical Review B - Condensed Matter and Materials Physics*, 84(17) <https://doi.org/10.1103/PhysRevB.84.174411>

This Article is brought to you for free and open access by the Department of Physics & Astronomy at LSU Digital Commons. It has been accepted for inclusion in Faculty Publications by an authorized administrator of LSU Digital Commons. For more information, please contact [ir@lsu.edu](mailto:ir@lsu.edu).

---

**Authors**

Biao Hu, Gregory T. McCandless, V. O. Garlea, S. Stadler, Yimin Xiong, Julia Y. Chan, E. W. Plummer, and R. Jin



# CHORUS

This is the accepted manuscript made available via CHORUS. The article has been published as:

## Structure-property coupling in $\text{Sr}_{\{3\}}(\text{Ru}_{\{1-x\}}\text{Mn}_{\{x\}})_{\{2\}}\text{O}_{\{7\}}$

Biao Hu, Gregory T. McCandless, V. O. Garlea, S. Stadler, Yimin Xiong, Julia Y. Chan, E. W. Plummer, and R. Jin

Phys. Rev. B **84**, 174411 — Published 11 November 2011

DOI: [10.1103/PhysRevB.84.174411](https://doi.org/10.1103/PhysRevB.84.174411)

# Structure-Property Coupling in $\text{Sr}_3(\text{Ru}_{1-x}\text{Mn}_x)_2\text{O}_7$

Biao Hu<sup>1</sup>, Gregory T. McCandless<sup>2</sup>, V. O. Garlea<sup>3</sup>, S. Stadler<sup>1</sup>,  
Yimin Xiong<sup>1</sup>, Julia Y. Chan<sup>2</sup>, E. W. Plummer<sup>1</sup> and R. Jin<sup>1,\*</sup>

<sup>1</sup>*Department of Physics & Astronomy, Louisiana State University, Baton Rouge, Louisiana 70803, USA*

<sup>2</sup>*Department of Chemistry, Louisiana State University, Baton Rouge, Louisiana 70803, USA and*

<sup>3</sup>*Neutron Scattering Sciences Division, Oak Ridge National Laboratory, Oak Ridge, Tennessee 37831, USA*

Layered ruthenates are prototype materials for the study of structure-property correlations. We report the structural and physical properties of double-layered perovskite  $\text{Sr}_3(\text{Ru}_{1-x}\text{Mn}_x)_2\text{O}_7$  single crystals with  $0 \leq x \leq 0.7$ . Single crystal x-ray diffraction refinements reveal that Mn doping on the Ru site leads to the shrinkage of unit-cell volume and disappearance of  $(\text{Ru}/\text{Mn})\text{O}_6$  octahedron rotation when  $x > 0.16$ , but the crystal structure remains tetragonal. Upon doping, the electrical resistivity reveals metallic character ( $d\rho/dT > 0$ ) at high temperatures but insulating behavior ( $d\rho/dT < 0$ ) below a characteristic temperature  $T_{\text{MIT}}$ . Interestingly,  $T_{\text{MIT}}$  is different from  $T_{\text{M}}$ , at which magnetic susceptibility reaches maximum. While  $T_{\text{MIT}}$  monotonically increases with increasing  $x$ ,  $T_{\text{M}}$  shows non-monotonic dependence with  $x$  even though the effective spin increases from  $S \sim 1$  ( $x=0$ ) to  $\sim 3/2$  ( $x=0.7$ ). The phase diagram consists of three distinct magnetic ground states, due to local structure change.

PACS numbers: 74.70.Pq, 71.30.+h, 71.27.+a, 61.05.cp

Transition metal oxides (TMOs) have attracted considerable attention due to the strong correlations between charge, lattice, orbital, and spin degrees of freedom. The Ruddleson-Popper (RP)  $\text{Sr}_{n+1}\text{Ru}_n\text{O}_{3n+1}$  ( $n$ =integer) series are prototype strongly correlated systems, since both theoretical and experimental investigations indicate intimate relationships between structural, electronic and magnetic properties [1–5]. A change in local structure often results in different ground states, as seen in single-layered ( $n=1$ )  $\text{Ca}_{2-x}\text{Sr}_x\text{RuO}_4$  [6, 7]. Different from the rest of the RP series,  $\text{Sr}_3\text{Ru}_2\text{O}_7$  ( $n=2$ ) shows unique physical properties. Although the electrical resistivity varies smoothly with temperature without any anomaly, the magnetic susceptibility of  $\text{Sr}_3\text{Ru}_2\text{O}_7$  reveals a characteristic peak around 16 K [2]. While density functional calculations predict that  $\text{Sr}_3\text{Ru}_2\text{O}_7$  is an itinerant system with ferromagnetic (FM) ordering tendencies [8], neutron scattering measurements confirm that the susceptibility peak corresponds to a short-range antiferromagnetic (AFM) correlation [9, 10]. Under the application of hydrostatic pressure, the ground state of  $\text{Sr}_3\text{Ru}_2\text{O}_7$  reveals FM instability [2]. On the other hand, the application of magnetic field leads to a metamagnetic transition at low temperatures [11]. These phenomena strongly suggest that both AFM and FM interactions are inherent in  $\text{Sr}_3\text{Ru}_2\text{O}_7$ .

It was reported that a small substitution of Ru by Mn drives the ground state from a paramagnetic metal (PM) to an AFM insulator (Mott type), and

a phase diagram of  $\text{Sr}_3(\text{Ru}_{1-x}\text{Mn}_x)_2\text{O}_7$  was mapped out up to  $x=0.2$  [12]. X-ray absorption spectroscopy (XAS) indicated that the Mn dopant has an oxidation state different from  $\text{Ru}^{4+}$  [13], while x-ray photoemission spectroscopy (XPS) showed no sign of doping-induced multiple Ru valences up to  $x=0.2$  [14]. We have studied  $\text{Sr}_3(\text{Ru}_{1-x}\text{Mn}_x)_2\text{O}_7$  over an extended doping range with  $0 \leq x \leq 0.7$ . According to its electronic and magnetic properties, a phase diagram is constructed which has two phase boundaries: one is a metal-insulator crossover line and the other is the magnetic transition line, even though they start off together at low doping levels as reported previously [12]. Through our results, we address the central issue: how Mn doping leads to the change of ground state properties.

Single crystals of  $\text{Sr}_3(\text{Ru}_{1-x}\text{Mn}_x)_2\text{O}_7$  ( $0 \leq x \leq 0.7$ ) were grown by the floating-zone technique in an image furnace. To avoid oxygen deficiency, 10 atmosphere oxygen pressure is applied during the growth. All selected crystals for physical property measurements shown here were characterized by powder and single crystal x-ray diffraction (XRD). The crystal structure and Mn concentration ( $x$ ) were determined by single crystal XRD refinement. Magnetic susceptibility measurements were carried out in a SQUID magnetometer. Measurements of the resistivity and specific heat were performed in a PPMS.

For all  $\text{Sr}_3(\text{Ru}_{1-x}\text{Mn}_x)_2\text{O}_7$  samples, single crystal XRD data show that their structure can be described by the space group  $I4/mmm$  with the details described previously [15]. Fig. 1(a) displays the unit-cell representation of  $\text{Sr}_3(\text{Ru}_{1-x}\text{Mn}_x)_2\text{O}_7$  and Fig. 1(b) illustrates the three oxygen sites of the  $(\text{Ru}/\text{Mn})\text{O}_6$  octahedron. Fig. 1(c) shows the  $x$  dependence of lat-

---

\*Electronic address: rjin@lsu.edu

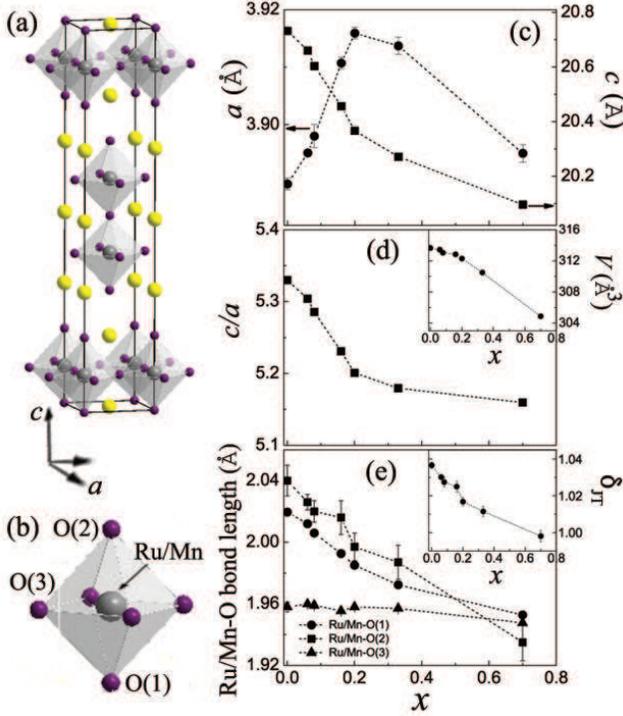


FIG. 1: (Color online) Unit-cell representation of  $\text{Sr}_3(\text{Ru}_{1-x}\text{Mn}_x)_2\text{O}_7$  in space group  $I4/mmm$  (a) and the configuration of the  $(\text{Ru}/\text{Mn})\text{O}_6$  octahedron (b), where the Mn atoms partially occupy the Ru site. (c)-(e) are the  $x$  dependence of the lattice parameters  $a$  and  $c$ , the ratio  $c/a$  and the rotation angle  $\phi$  of the  $(\text{Ru}/\text{Mn})\text{O}_6$  octahedron and the bond lengths of Ru/Mn-O(1) (inner apical), Ru/Mn-O(2) (outer apical), and Ru/Mn-O(3) (equatorial) at 298 K. The insets of (c) and (e) are the unit cell volume  $V$  and the Jahn-Teller distortion  $\delta_{\text{JT}}$  as a function of  $x$  at 298 K, respectively. Dashed lines are guides for the eye.

tice parameters  $a$  and  $c$  at 298 K. Note that, with increasing  $x$ ,  $a$  increases for  $0 \leq x \leq 0.2$  and decreases for  $x > 0.2$ , while  $c$  decreases monotonically. This results in a monotonic decrease of the unit cell volume  $V$  (see the inset of Fig. 1(d)) and  $c/a$  with increasing  $x$ , as shown in Fig. 1(d). According to Ref. [16] the volume obtained from polycrystalline  $\text{Sr}_3\text{Mn}_2\text{O}_7$  ( $x=1$ ) is even smaller. This suggests that the ionic radius of Mn is smaller than that of Ru. Remarkably, the Ru/Mn-O(3) bond length remains more or less unchanged, while both the Ru/Mn-O(1) and Ru/Mn-O(2) bond lengths [Fig. 1(e)] decrease with increasing  $x$ . The Jahn-Teller distortion ( $\delta_{\text{JT}}$ ) can be calculated via  $\delta_{\text{JT}} = [\text{Ru}/\text{Mn}-\text{O}(1) + \text{Ru}/\text{Mn}-\text{O}(2)] / [2 \times \text{Ru}/\text{Mn}-\text{O}(3)]$ , which decreases from 1.04 for  $x=0$  to 1.00 for  $x=0.7$  (see the inset of Fig. 1(e)). This indicates that Mn doping makes the  $(\text{Ru}/\text{Mn})\text{O}_6$  octahedron less distorted. Further support can be found from the reduction of rotation angle of the  $(\text{Ru}/\text{Mn})\text{O}_6$  octahedron, as will be discussed later.

The temperature dependence of the in-plane electrical resistivity ( $\rho_{\text{ab}}$ ) of  $\text{Sr}_3(\text{Ru}_{1-x}\text{Mn}_x)_2\text{O}_7$  is shown in Fig. 2(a). For the undoped compound ( $x=0$ ),  $\rho_{\text{ab}}(T)$  is metallic in the measured temperature range. Upon doping,  $\rho_{\text{ab}}$  is not only enhanced in magnitude but also changes the sign in slope at a characteristic temperature  $T_{\text{MIT}}$  from positive (metallic) at high temperatures to negative (insulating) at low temperatures. The out-of-plane electrical resistivity ( $\rho_c$ ) exhibits very similar temperature and  $x$  dependence (not shown), but there is a large anisotropy as shown in the inset of Fig. 2(a). This result is consistent with the previous report that a metal-insulator transition (MIT) occurs when introducing the Mn dopant into  $\text{Sr}_3\text{Ru}_2\text{O}_7$  [12]. With increasing  $x$ ,  $T_{\text{MIT}}$  is quickly pushed to higher temperatures and the transition becomes less pronounced.

However, the magnetic properties of  $\text{Sr}_3(\text{Ru}_{1-x}\text{Mn}_x)_2\text{O}_7$  reveal a different trend. Fig. 2(b) shows the temperature dependence of the in-plane magnetic susceptibility ( $\chi_{\text{ab}}$ ) under zero-field cooling (ZFC) ( $\chi_{\text{ab}}$  measured under the field-cooling condition is very similar). For  $0 \leq x \leq 0.7$ ,  $\chi_{\text{ab}}$  always displays a characteristic peak at  $T_{\text{M}}$ . For  $x=0$ ,  $T_{\text{M}}$  is about 16 K, in agreement with previous results [2]. With increasing  $x$ ,  $T_{\text{M}}$  initially increases then decreases, with a maximum ( $\sim 80$  K) near  $x \sim 0.16$ . The out-of-plane magnetic susceptibility ( $\chi_c$ ) reveals (not shown) very similar temperature and  $x$  dependence as  $\chi_{\text{ab}}$  and has almost identical value at 300 K for  $x > 0.16$  (see the inset of Fig. 2(a)).

The resistivity and magnetic susceptibility data reveal two characteristic temperatures ( $T_{\text{MIT}}$  and  $T_{\text{M}}$ ) in  $\text{Sr}_3(\text{Ru}_{1-x}\text{Mn}_x)_2\text{O}_7$ . The question is whether they correspond to true phase transitions. The specific heat data shown in Fig. 2(c) allow us to determine the nature of  $T_{\text{MIT}}$  and  $T_{\text{M}}$ . In Fig. 2(c), we plot the specific heat as  $C_{\text{p}}/T$  vs  $T$ , and shift the data for each doping level for clarity. For each  $x$ , the value of  $C_{\text{p}}$  at  $T = 2$  K is plotted in the inset of Fig. 2(c). For  $x=0$ ,  $C_{\text{p}}$  varies with  $T$  smoothly without any anomaly at  $T_{\text{M}} \sim 16$  K. This indicates that there is no true phase transition in the undoped compound, consistent with neutron scattering measurements [9]. For  $x=0.06$ , there is a clear specific heat anomaly at  $T_{\text{M}}$ , indicating a true second order phase transition. Since  $T_{\text{M}} \sim T_{\text{MIT}}$  for  $x=0.06$ , it is unclear whether the phase transition originates from magnetic ordering and/or a metal-insulator transition. Specific heat data for higher doping levels can clarify this. Note that, for  $x=0.16$ , the specific heat anomaly presents at  $T_{\text{M}} \sim 80$  K but not at  $T_{\text{MIT}} \sim 140$  K. This indicates that  $T_{\text{M}}$  in the region of  $0.06 \leq x \leq 0.16$  corresponds to a true phase transition, while  $T_{\text{MIT}}$  represents a crossover temperature from metallic behavior at high temperatures to

insulating character at low temperatures. Recent neutron scattering experiments confirm long-range AFM ordering below  $T_M$  for  $x=0.16$  [17].

Theoretically, the entropy removal upon magnetic ordering is expected to be  $S_M=R\ln(2S+1)=1.09R$  for  $S=1$  and  $1.39R$  for  $S=3/2$  ( $R=8.314$  J/mol K). We may estimate the actual entropy removal at  $T_M$  by subtracting the background by fitting the experimental data outside of the transition region using a polynomial (dashed line in Fig. 2(c)). By integrating  $\Delta C_p/T$  in the transition region, we obtain  $\Delta S_M \sim 0.077R$  for  $x=0.06$ ,  $0.64R$  for  $x=0.08$ , and  $0.77R$  for  $x=0.16$ . These values are considerably smaller than the expected values, indicating that only a fraction of the spins are ordered. It is also possible that some of entropy has been removed above  $T_M$ . Nevertheless, the specific heat anomaly at  $T_M$  can no longer be detected when  $x>0.16$  (see the inset of Fig. 2(c)), suggesting that there is no long-range magnetic ordering at high Mn doping levels. As shown in the inset of Fig. 2(c), the low temperature (2 K) specific heat decreases with increasing  $x$ , quickly dropping to a very small value as  $x>0.16$ . This is most likely due to the reduction of electronic specific heat, because of the insulating ground state when  $x \neq 0$ . The electronic specific heat becomes negligible at high Mn doping concentrations.

In order to understand why  $T_M$  varies with  $x$  non-monotonically, we analyze  $\chi_{ab}$  and  $\chi_c$  at high temperatures. Both  $\chi_{ab}(T)$  and  $\chi_c(T)$  can be fitted with a formula  $\chi(T)=\chi_0+\chi_{CW}(T)$  between 175 K and 390 K. Here  $\chi_0$  is the temperature independent term and  $\chi_{CW}(T)=C/(T-\Theta_{CW})$  is the Curie-Weiss term with Curie constant  $C=N_A p_{\text{eff}}^2 \mu_B^2 / (3k_B)$  and Curie-Weiss temperature  $\Theta_{CW}$  ( $p_{\text{eff}}$  is the effective Bohr magneton number,  $\mu_B$  is the Bohr magneton, and  $k_B$  is the Boltzmann constant). Although not shown, the above formula fits our experimental data very well with standard deviation about 0.1%. For all compounds,  $\chi_0$  is more or less constant, in the order of  $0.5 \times 10^{-3}$  cm<sup>3</sup>/mol. Plotted in Fig. 3 is the  $x$  dependence of  $p_{\text{eff}}$  (main panel) and  $\Theta_{CW}$  (inset). Note that both  $\Theta_{CW}^{ab}$  and  $\Theta_{CW}^c$  are negative with similar magnitude and increase with increasing  $x$  for  $0 \leq x \leq 0.16$ . For  $x > 0.2$ ,  $\Theta_{CW}^{ab}$  is positive but  $\Theta_{CW}^c$  remains negative. The sign change of  $\Theta_{CW}^{ab}$  is likely caused by the change from AFM to FM interaction in the  $ab$  plane, while the dominant magnetic interaction in  $c$  direction remains AFM. Indeed, the in-plane magnetization ( $M_{ab}$ ) vs field ( $H$ ) plot shows FM character when  $x > 0.16$  (see the inset of Fig. 2(b)). The above fitting also shows that  $p_{\text{eff}}^{ab} \sim p_{\text{eff}}^c$ . Remarkably, both  $p_{\text{eff}}^{ab}$  and  $p_{\text{eff}}^c$  increase with  $x$  and tend to saturate for  $x > 0.16$ . For  $x=0$ ,  $p_{\text{eff}} \sim 2.8$ , corresponding to  $S=1$ , according to  $p_{\text{eff}}=g\sqrt{S(S+1)}$  with  $g=2$  for transition metals.

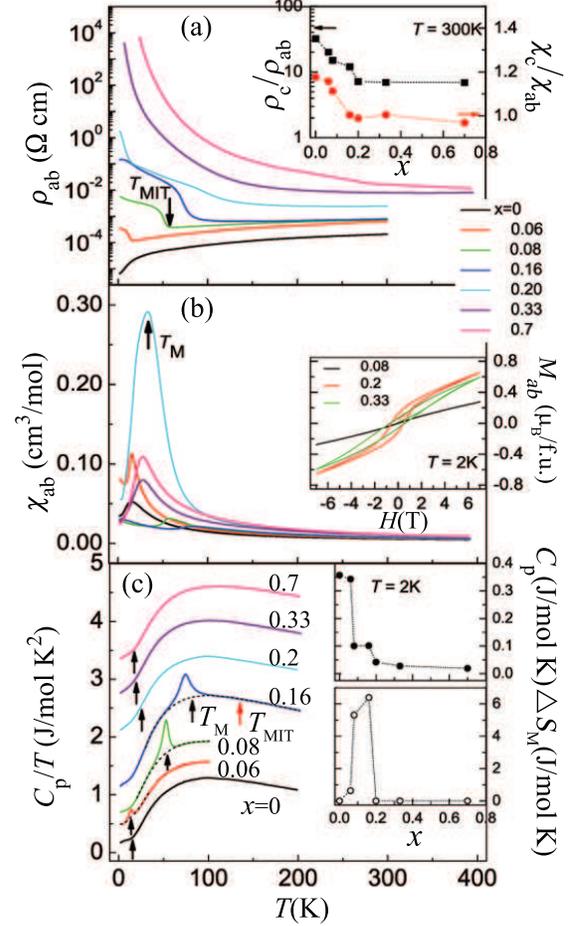


FIG. 2: (Color online) (a) is the temperature dependence of  $\rho_{ab}(T)$  with different  $x$ . The arrow shows an example of the temperature defined as  $T_{MIT}$  for  $x=0.08$ . The inset shows the  $x$  dependence of  $\rho_c/\rho_{ab}$  and  $\chi_c/\chi_{ab}$  at 300 K. (b) is  $\chi_{ab}$  as a function of  $T$  with different  $x$ . The arrow shows an example of the temperature defined as  $T_M$  for  $x=0.2$ . The inset displays in-plane magnetization  $M_{ab}(H)$  hysteresis loops at 2 K for  $x=0.08$  (black), 0.2 (red) and 0.33 (green). (c) Temperature dependence of specific heat  $C_p$  of  $\text{Sr}_3(\text{Ru}_{1-x}\text{Mn}_x)_2\text{O}_7$ , plotted as  $C_p(T)/T$  versus  $T$  and shifted for clarity. The black arrows indicate  $T_M$  for each concentration. The red arrow indicates  $T_{MIT}$  for  $x=0.16$ . Dashed lines for each  $x$  represent the polynomial fit to the specific heat background. The insets show  $C_p$  at 2 K (top) and entropy change at  $T_M$  (bottom) for each  $x$ .

For  $x > 0.16$ ,  $p_{\text{eff}} \sim 3.7$ , corresponding to  $S=3/2$ .

Based on the above observations, we construct a phase diagram for  $\text{Sr}_3(\text{Ru}_{1-x}\text{Mn}_x)_2\text{O}_7$ , covering  $0 \leq x \leq 0.7$ . Fig. 4 shows the  $x$ - $T$  phase diagram, which consists of two boundary lines:  $T_{MIT}$  and  $T_M$ . In terms of physical properties, it can be divided into five regions, as marked in the phase diagram. Region I represents a paramagnetic (PM) metallic (PM-M) phase, which covers temperature range above  $T_{MIT}$ . Region II is a PM insulating (PM-I) phase, where the sys-

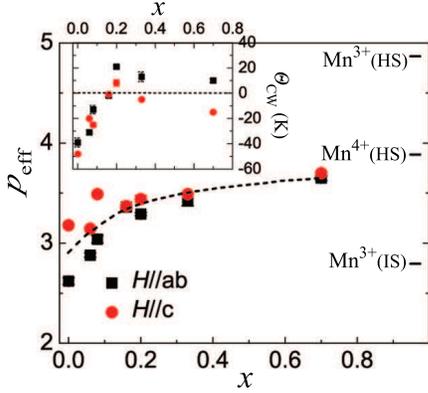


FIG. 3: (Color online)  $x$  dependence of the derived  $p_{\text{eff}}$  from Curie-Weiss law fitting under  $H\parallel ab$  and  $H\parallel c$ . Dashed lines are guides for the eye.  $p_{\text{eff}}$  for different Mn oxidation states is also indicated: HS = high spin, IS = intermediate spin. The inset represents the  $x$  dependence of the derived  $\Theta_{\text{CW}}$ .

tem is non-metallic with  $d\rho/dT < 0$  but remains paramagnetic. Region III ( $0 \leq x < 0.06$ ) represents metallic phase with AFM correlation (AFMC-M), which is enhanced upon Mn doping. Region IV is a long-range (LR) AFM insulating (LR-AFM-I) phase, where LR AFM ordering forms below  $T_M$  and the specific heat anomaly emerges at  $T_M$ . Since there is lack of specific heat anomaly, Region V is an insulating phase with short-range magnetic (FM in the  $ab$  plane and AFM in the  $c$  direction) correlations (SRMC-I). It should be pointed out that there is no conflict between our phase diagram and what presented in Ref [12]. In low doping regime,  $T_{\text{MIT}} \sim T_M$ , resulting in single boundary line [12].

In light of all of the structural and physical properties, it becomes clear that the variation of electronic and magnetic properties is intimately connected with the change of local structure of  $\text{Sr}_3(\text{Ru}_{1-x}\text{Mn}_x)_2\text{O}_7$  even though the global structure symmetry remains unchanged. Due to the partial replacement of Ru by Mn with smaller ionic radius, the unit cell becomes smaller and (Ru/Mn) $\text{O}_6$  becomes less distorted. This is reflected in both rotation angle (see Fig. 4) and Jahn-Teller distortion parameter  $\delta_{\text{JT}}$  (see the inset of Fig. 1 (e)). This weakens the FM interaction, according to the theoretical calculations for the single layered ruthenate  $\text{Ca}_{2-x}\text{Sr}_x\text{RuO}_4$  [5], and leads to long-range AFM ordering in Region IV. When  $x > 0.16$ , (Ru/Mn) $\text{O}_6$  no longer rotates which gives rise to competitive AFM and FM interactions (see the inset of Fig. 3). As a result, the system can no longer form long-range magnetic ordering (Region V). On the other hand, the increase of  $T_{\text{MIT}}$  with  $x$  is not surprising, as  $3d$ -Mn is more localized than  $4d$ -Ru.

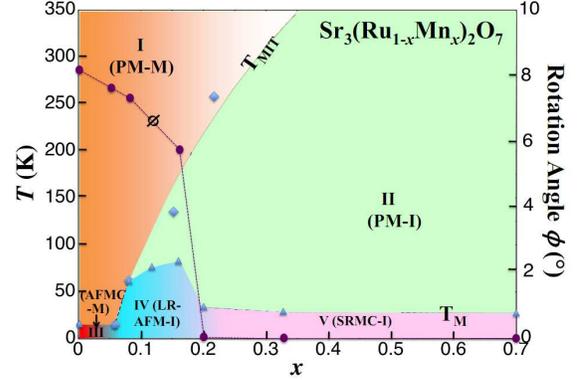


FIG. 4: (Color online) The  $x$ - $T$  phase diagram of  $\text{Sr}_3(\text{Ru}_{1-x}\text{Mn}_x)_2\text{O}_7$  ( $0 \leq x \leq 0.7$ ). Diamonds and triangles represent  $T_{\text{MIT}}$  and  $T_M$ , respectively. Region I is a paramagnetic metallic (PM-M) phase. Region II is a paramagnetic insulating (PM-I) phase. Region III is a metallic phase with AFM correlation (AFMC-M). Region IV represents a long-range AFM insulating phase (LR-AFM-I). Region V is an insulating phase with short-range magnetic correlation (SRMC-I). The right axis shows the  $x$  dependence of the rotation angle  $\phi$  of the (Ru/Mn) $\text{O}_6$  octahedron at 90 K.

What is remarkable is that small amount of Mn doping can drive the system into an insulating ground state. In previous studies, optical conductivity spectra reveal evidence for Mott-type metal-insulator transition [12]. This suggests that Mn doping narrows the bandwidth thus enhancing electron-electron correlation. Is band filling also changed? According to XAS data, Mn acts as  $3+$  in  $\text{Sr}_3(\text{Ru}_{0.9}\text{Mn}_{0.1})_2\text{O}_7$  [13]. If this were the case, one would expect (1) expansion of the lattice unit cell as  $\text{Mn}^{3+}$  ( $0.65\text{\AA}$ ) has large ionic radius than  $\text{Ru}^{4+}$  ( $0.62\text{\AA}$ ), (2) effective  $S \sim 2$  for high spin (HS) state or  $S=1$  for intermediate spin (IS) state, (3) Ru would exhibit  $5+$  valence, or (4) oxygen deficiency while Ru remains  $4+$ . Scenarios (1), (2) and (3) may be ruled out, since (1) our XRD data reveal the shrinkage of the unit cell (Fig. 1(c)), (2) high-temperature magnetic susceptibility indicates the increase of  $S$  from 1 at  $x=0$  to  $\sim 3/2$  at  $x=0.7$  (Fig. 3), and (3) XPS data exhibit no change in Ru spectra for Mn-doped compounds [14]. On the other hand, scenario (4) is also unlikely as all of our single crystal samples were grown under 10 atmosphere oxygen pressure and our single crystal x-ray refinement provides no evidence for oxygen deficiency. Thus, it is most likely that the oxidation state of Mn in  $\text{Sr}_3(\text{Ru}_{1-x}\text{Mn}_x)_2\text{O}_7$  is  $4+$ , independent of  $x$ . Thus, Mn doping in  $\text{Sr}_3(\text{Ru}_{1-x}\text{Mn}_x)_2\text{O}_7$  is isovalent while band filling remains unchanged.

In summary, we have investigated the structural and physical properties of Mn-doped  $\text{Sr}_3\text{Ru}_2\text{O}_7$  and constructed a rich phase diagram for  $0 \leq x \leq 0.7$ . Two

characteristic temperatures ( $T_{\text{MIT}}$  and  $T_{\text{M}}$ ) are required to accurately describe the change of the physical properties.  $T_{\text{MIT}}$  shows a monotonic change, while  $T_{\text{M}}$  reveals a non-monotonic dependence with  $x$ . Three distinct regions are identified below  $T_{\text{M}}$ , which is driven by the local structure change. This work illustrates that isovalent doping is an effective approach for studying correlated effect on physical properties.

Work at LSU was partially supported by US National Science Foundation with Grant Nos. DMR-1002622 (B. H., E. W. P., and R. J.) and DMR-1063735 (J. Y. C.). The work at the High Flux Isotope Reactor, Oak Ridge National Laboratory, was sponsored by the Scientific User Facilities Division, Office of Basic Energy Sciences, U.S. Department of Energy.

- 
- [1] Y. Maeno, H. Hashimoto, K. Yoshida, S. Nishizaki, T. Fujita, J. G. Bednorz, and F. Lichtenberg, *Nature (London)* **372**, 532 (1994).
- [2] S. I. Ikeda, Y. Maeno, S. Nakatsuji, M. Kosaka, and Y. Uwatoko, *Phys. Rev. B* **62**, R6089 (2000).
- [3] D. Fobes, M. H. Yu, M. Zhou, J. Hooper, C. J. O'Connor, M. Rosario, and Z. Q. Mao, *Phys. Rev. B* **75**, 094429 (2007).
- [4] G. Cao and P. Schlottmann, *Mod. Phys. Lett.* **22**, 1785 (2008).
- [5] Z. Fang and K. Terakura, *Phys. Rev. B* **64**, 020509 (2001).
- [6] S. Nakatsuji and Y. Maeno, *Phys. Rev. Lett.* **84**, 2666 (2000).
- [7] O. Friedt, M. Braden, G. Andre, P. Adelman, S. Nakatsuji, and Y. Maeno, *Phys. Rev. B* **63**, 174432 (2001).
- [8] D. J. Singh and I. I. Mazin, *Phys. Rev. B* **63**, 165101 (2001).
- [9] L. Capogna, E. M. Forgan, S. M. Hayden, A. Wildes, J. A. Duffy, A. P. Mackenzie, R. S. Perry, S. Ikeda, Y. Maeno, and S. P. Brown, *Phys. Rev. B* **67**, 012504 (2003).
- [10] M. B. Stone, M. D. Lumsden, R. Jin, B. C. Sales, D. Mandrus, and S. E. Nagler, *Phys. Rev. B* **73**, 174426 (2006).
- [11] R. S. Perry, L. M. Galvin, S. A. Grigera, L. Capogna, A. J. Schofield, A. P. Mackenzie, M. Chiao, S. R. Julian, S. I. Ikeda, S. Nakatsuji, Y. Maeno, and C. Pfleiderer, *Phys. Rev. Lett.* **86**, 2661 (2001).
- [12] R. Mathieu, A. Asamitsu, Y. Kaneko, J. P. He, X. Z. Yu, R. Kumai, Y. Onose, N. Takeshia, T. Arima, H. Takagi, and Y. Tokura, *Phys. Rev. B* **72**, 092404 (2005).
- [13] M. A. Hossain, Z. Hu, M. W. Haverkort, T. Burnus, C. F. Chang, S. Klein, J. D. Denlinger, H.-J. Lin, C. T. Chen, R. Mathieu, Y. Kaneko, Y. Tokura, S. Satow, Y. Yoshida, H. Takagi, A. Tanaka, I. S. Elfimov, G. A. Sawatzky, L. H. Tjeng, and A. Damascelli, *Phys. Rev. Lett.* **101**, 016404 (2008).
- [14] H. Guo, Yi Li, Darwin Urbina, Biao Hu, Rongying Jin, Tijiang Liu, David Fobes, Zhiqiang Mao, E. W. Plummer, and Jiandi Zhang, *Phys. Rev. B* **81**, 155121 (2010).
- [15] B. Hu, Gregory T. McCandless, Melissa Menard, V. B. Nascimento, Julia Y. Chan, E. W. Plummer, and R. Jin, *Phys. Rev. B* **81**, 184104 (2010).
- [16] J. F. Mitchell, J. E. Millburn, M. Medarde, S. Short, J. D. Jorgensen, and M. T. Fernandez-Diaz, *J. Solid State Chem.* **141**, 599 (1998).
- [17] D. Mesa, F. Ye, S. Chi, J. Fernandez-Baca, B. Hu, R. Jin, E. W. Plummer, and Jiandi Zhang, Unpublished